

Thermo Mechanical Analysis of Coated Engine Valve Using Finite Element Method

Vipul Wadhwa¹, Ajay Kumar²

¹ M.Tech. Student, Ambala College of engineering and Applied Research, Mithapur, Ambala

² Assistant Professor, Dept. of Mechanical Engg. Ambala College of engineering and Applied Research, Mithapur, Ambala

Email: vipulwadhwa3420@gmail.com

Abstract- Surface coating technology has emerged as a reliable technique for increasing component life. Coating material and coating thickness evaluation for different conditions is foremost requirement. The present study aims to evaluate engine valve life using the coating technology as well as computer aided engineering. The work begins with selection of engine valve and thermal barrier coatings. Five surface coating of different material were studied at three coating thickness i.e. 100 microns, 150 microns and 200 microns for compiling a comparative database. 3D modeling of engine valve for uncoated and for different coating thickness was done on ANSYS software. Analysis was performed for calculating temperature distribution, Heat flux, stress and strain values. Outcome of above study suggested that the surface coating shows potential increase in engine life by reducing thermal softening and also provides shield to sliding and erosive wear. A comparative database has been formed for Temperature fall, stress and strain values for different coatings at various thickness in view to, for selection of suitable coating material and thickness. As result, CaZrO_3 is reported as best coating at 200 microns for engine valve.

Keywords- Engine, coating, heat flux, stress, strain

1. INTRODUCTION

Surface coating technology has emerged as a reliable technique for increasing life of components working under serve conditions. Thermal barrier coatings have shown proven results for lowering the thermal stress and wear of components such one component in current study in exhaust engine valve. Coating powder and coating thickness are important factors for lowering thermal stress and wear. In recent years, FEM analysis using IT tools has saved lot of time and money to obtain preliminary results

Thus objective in current work is to evaluate the performance of thermal barrier coated on existing material used for manufacturing engine valves using ANSYS and to provide a comparative database for selecting the coating powder and thickness.

2. ENGINE VALVE

Engine Valve is one of the main component of which is used in all IC Engines It allows burnt gases to escape from the cylinder to atmosphere. Figure 1 shows the engine valve

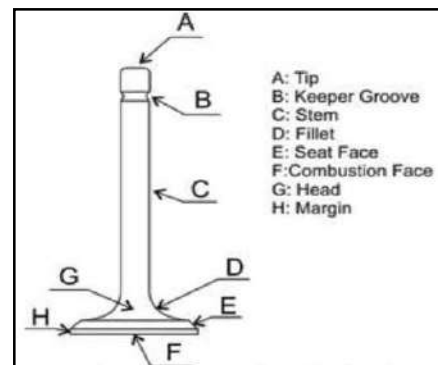


Figure 1 Descriptive image of Engine valve

An exhaust valve is subjected to:-

1. Longitudinal cyclic stresses due to the return spring load and the inertia response of the valve assembly.
2. Thermal stresses in the circumferential and longitudinal directions due to the large temperature gradient from the centre of the head to its periphery and from the crown to the stem. A typical variation of temperature in an exhaust valve is given in Figure 2
3. Creep conditions due to operation at very high temperatures, particularly in case of valve head.
4. Corrosion conditions.

Failure due to large temperature difference/ creep is stated as major reason of engine valve failure thus technique is required to reduce thermal stresses and

increase engine valve life. Figure 2 shows typical temperature distribution.

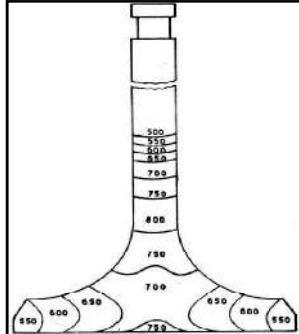


Figure 2 Typical temperature distributions in exhaust valve in degree Celsius
1.1 Engine valve modelling

In current study Exhaust valve of Maruti Swift 1.3 Litre engine is selected; valve material is special steel grade known as SUH 11. It is highly alloyed (Mn-Ni-Cr-Mo-N) largely used for inlet and exhaust valve for IC engines required properties of the material are listed in table 1. Figure 3 shows the specification of engine valve.

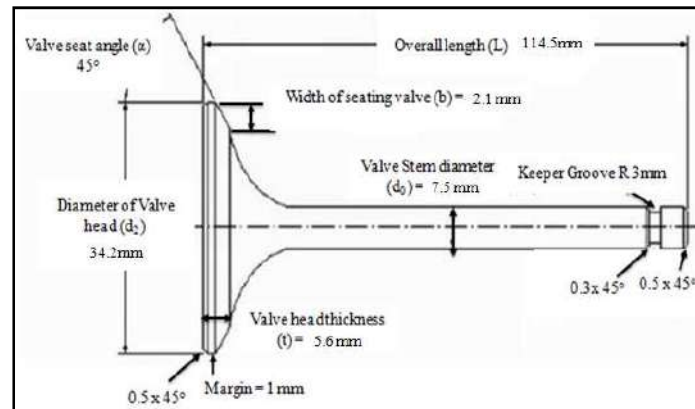


Figure 3. Specification of engine valve

Table 1 Properties of engine valve material

Type of material	SUH 11/ X50CrSi18-2
Young's modulus	200000 MPa
Tensile Strength	600 MPa
Fatigue strength	275 MPa
Yield Strength	250 MPa
Poisson Ratio	0.3
Density	7700 Kg/m ³
Thermal expansion	10 e-6 /K
Thermal Conductivity	25 W/m K
Specific heat	460 J/Kg K
Melting temperature	1450 OC

3. SURFACE COATINGS

Surface coating is an enabling technology that is applied to the surface of an object, usually referred to as the substrate. The purpose of applying the coating may be decorative, functional, or both. Functional coatings may be applied to change the surface properties of the substrate, such as

adhesion, wettability, corrosion resistance, or wear resistance. Such one category of coatings is thermal barrier coatings.

3.1 Thermal barrier coatings (TBC)

These are highly advanced materials systems usually applied to metallic surfaces operating at

elevated temperatures. These coatings serve to insulate components from large and prolonged heat loads by utilizing thermally insulating materials. In doing so, these coatings can allow for higher operating temperatures while limiting the thermal exposure of structural components, extending part life by reducing oxidation and thermal fatigue in conjunction with active film cooling. Figure 4 shows the structure of thermal barrier coating

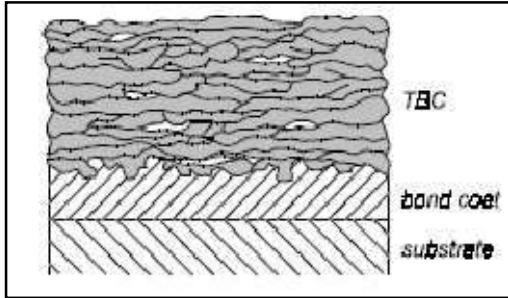


Figure 4. Shows the structure of surface coating

Thus thermal barrier coating could be the technique which can be used on engine valve guide for preventing them from creep failure.

3.2 Coating selection

Engine valve has to undergo under serve conditions such thermal shock; thermal softening, thermal fatigue and thermal wear and oxidation thus surface coat selected should be able to endure the conditions and provides its services. Depth literature survey has confirmed ceramic coatings can transform an ordinary metal into a high-performance surface applied by high energy Plasma, ceramics coatings give following benefits:-

- High hardness and durability
- Dense and pore free (sealed)
- Thermo-chemical bond strength
- Anti galling
- Electrical resistivity
- Thermal barrier coatings (TBC)
- Resistance to thermal shock

In current project five ceramic coatings are studied. Bond Coat is applied to improve the bond strength and thermal stress due to difference in thermal expansion coefficient of base material and surface coat NiCrAl is commonly used bond and is studied in current project. Properties of coatings and bond coat from literature are listed in table 2.

Table 2 Ceramic and Bond Coating properties

Property	Units	NiCrAl	MgZrO ₃	CaZrO ₃	SiC	Mullite (3Al ₂ O ₃ 2SiO ₂)	ZrO ₂ + Y ₂ O ₃
Density	Kg/m ³	7870	5600	5110	3210	2800	5560
Coefficient of thermal Expansion	C ⁻¹ Reference temperature 250C	1.20E-05	8.00E-06	3.20E-06	5.12E-06	5.50E-06	1.09E-05
Young's modulus	Mpa	90000	46000	1.00E+05	4.76E+05	1.51E+05	11250
Poisson's ratio		0.27	0.2	0.2	0.19	0.2	0.3
Bulk Modulus	Pa	6.52E+10	2.56E+10	5.56E+10	2.56E+11	8.39E+10	9.38E+09
Shear Modulus	Pa	3.54E+10	1.92E+10	4.17E+10	2.00E+11	6.29E+10	4.33E+09
Thermal Conductivity	Wm ⁻¹ C ⁻¹	1.61E+01	8.00E-01	6.00E-01	5.00E+00	6.00E+00	1.40E+00

4. ANALYSIS

In current project FEA is applied on solid CAD model of uncoated and coated valve with bond coat using coupled steady state thermal and static

structural analysis system. Figure 5 shows the coupled steady state thermal and static structural analysis. Figure 6 shows the 3d model of engine valve.

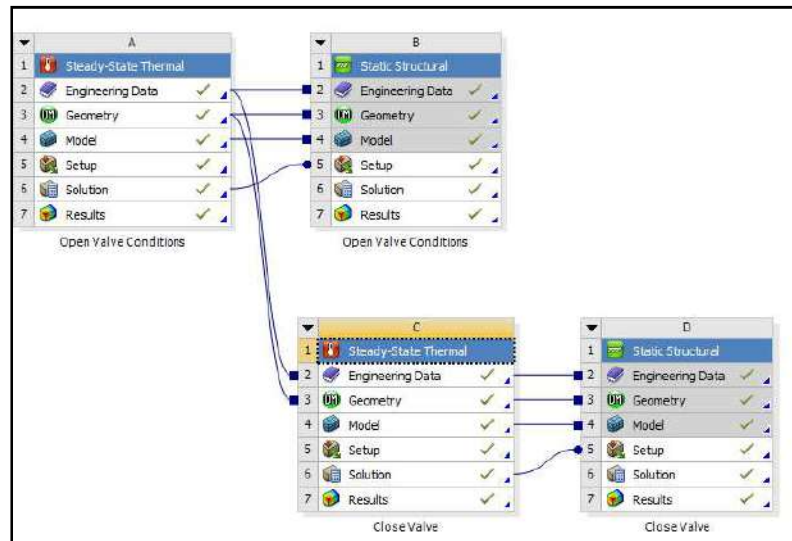


Figure5: Coupled Stead-State Thermal and Static structural analysis systems

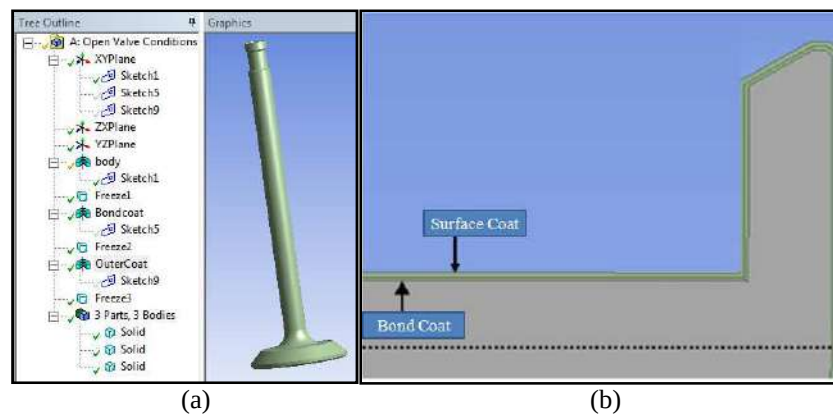


Figure 6 a) Generated model b) Cut section View of generated model

4.1 Boundary Conditions:

Steady –State thermal analysis

a) Open Valve Condition: Temperature at valve head 650°C and 500°C at Valve Stem with over all heat transfer coefficient of $500 \text{ W/m}^2\text{C}$

b) Closed Valve Condition: Temperature at valve head 650°C with over all heat transfer coefficient of $500 \text{ W/m}^2\text{C}$.

Static Structural Analysis

a) Open Valve Condition: Thermal condition imported from coupled steady state thermal analysis and gas pressure at valve head $5 \times 10^6 \text{ Pa}$ with net force of 1200N acting downward.

b) Closed Valve Condition: Thermal condition imported from coupled steady state thermal analysis and gas pressure at valve head $7 \times 10^6 \text{ Pa}$ with net force of 800N acting upward. Figure 7 shows applied boundary conditions.

5. SOLUTION

Engine valve is evaluated to obtain results for Temperature distribution, Heat flux, Von-Mises Stress and Elastic strain. Figure 8 shows the result plots for uncoated and $200 \mu\text{m}$ CaZrO_3 coated engine valve for open and close conditions.

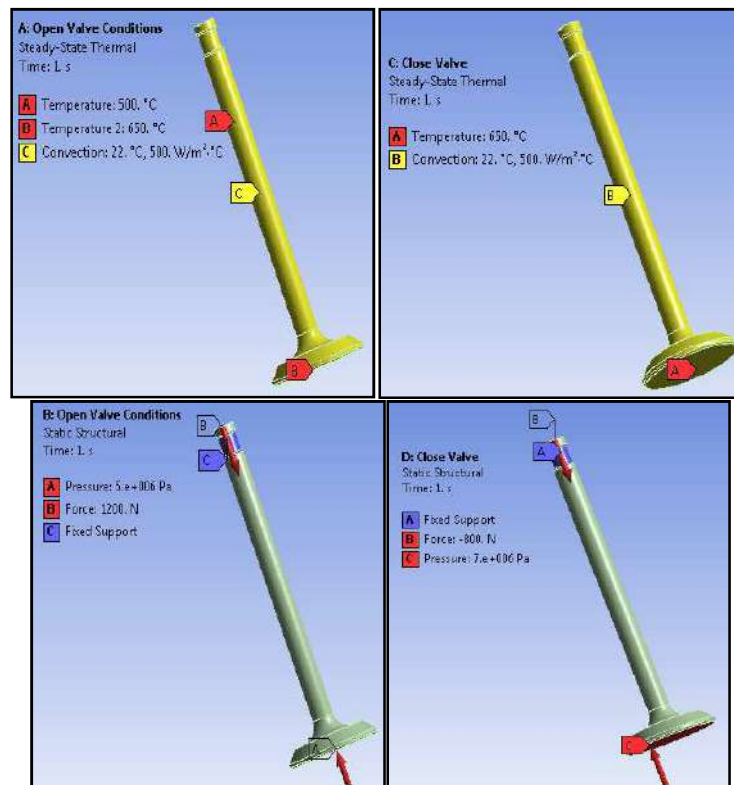


Figure 7 Applied Boundary conditions on engine valve

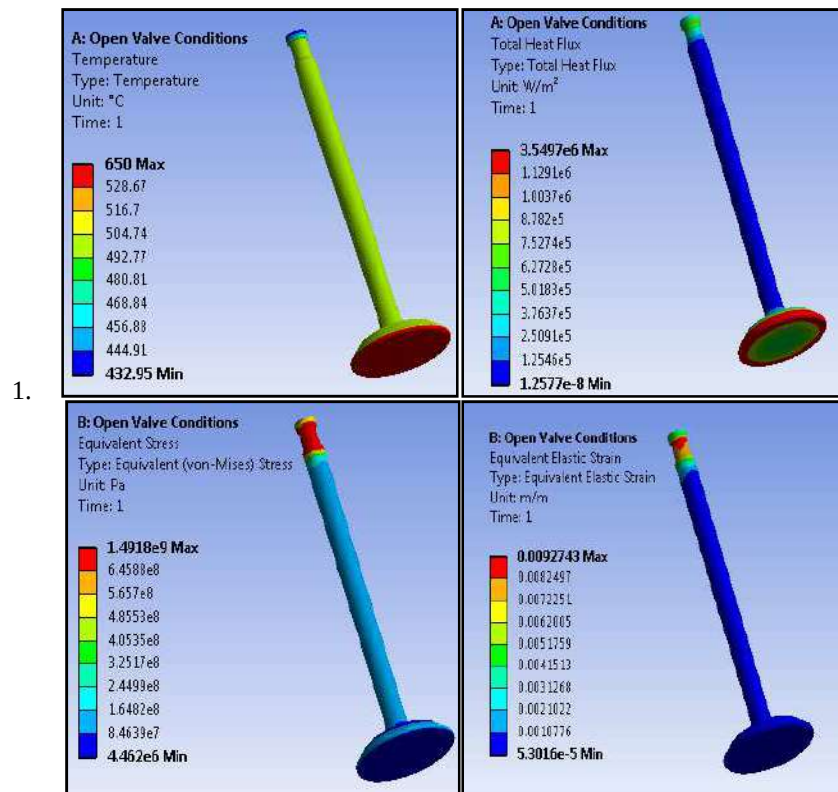


Figure 8 Results plots for uncoated engine valve in open state

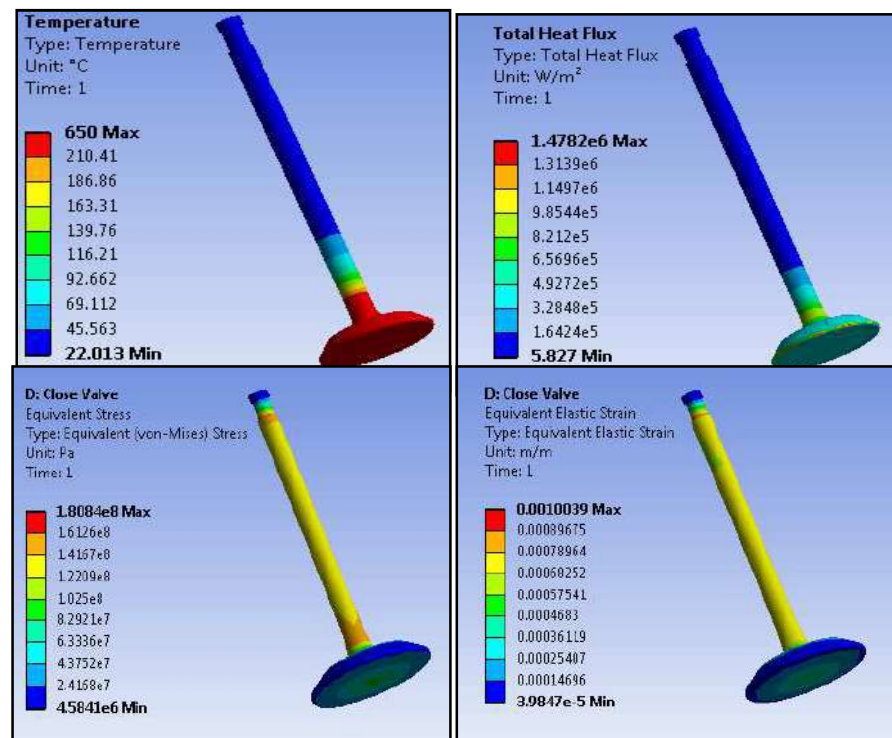


Figure 9 Results plots for uncoated engine valve in close state

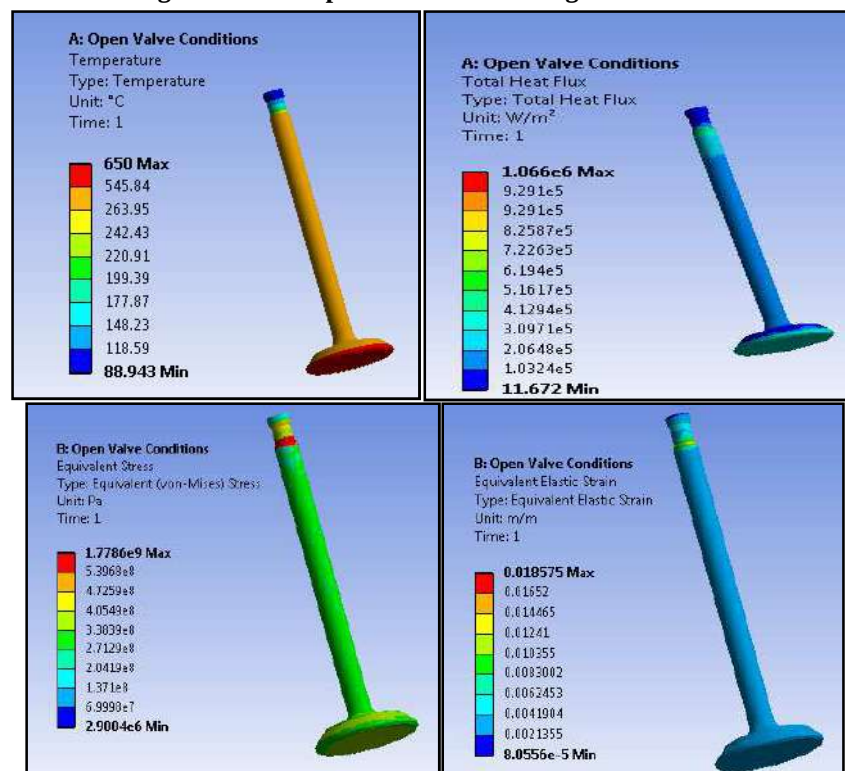


Figure 10 Results plots for open engine valve coated with 200 µm CaZrO₃

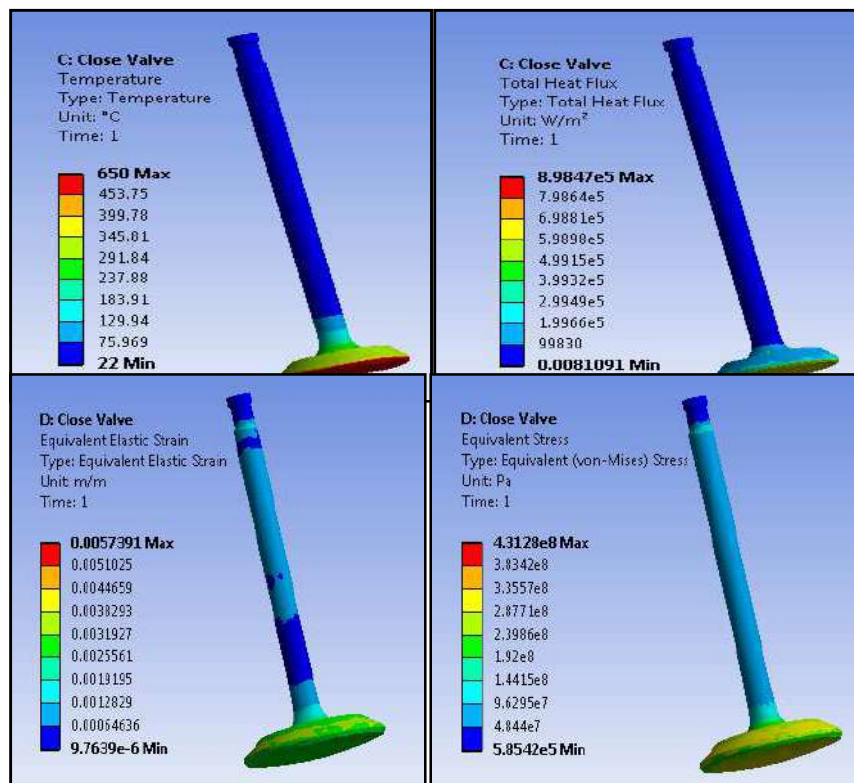


Figure 11 Results plots for closed engine valve coated with 200 μm CaZrO_3

6. RESULTS

In this work, engine valve is explored with thermal barrier coatings in order to enhance its performance and life. The work began with designing of engine valve and simultaneous properties of feasible surface coatings were listed. Engine valve is analysed for uncoated SUH11 material and with 5 different coatings. To acquire optimum coating thickness the coating is analysed for three coating thickness i.e. 100 μm , 150 μm and 200 μm . the work

involves computer aided engineering; design and analysis of engine valve is done ANSYS software package.

Analysis report of engine valve on the basis of Temperature, Heat flux, equivalent Von-Mises stress and Strain is compiled in table 3 and table 4 for open valve state and close valve state. Important Graphs plotted from analysis results are shown in figure 12.


Table 3 Compiled Analysis report for Engine Valve in open state

Valve Details	Coating Thickness (μm)	Temperature (°C)		Heat Flux (W/m^2)		Equivalent von-Mises Stress (MPa)		Strain	
		Max	Min	Max	Min	Max	Min	Max	Min
Uncoated	0	650	432.9	3.55E+06	1.26E-08	1.49E+03	4.462	0.0092743	5.31E-05
$\text{ZrO}_2 + 8\% \text{Y}_2\text{O}_3$	100	650	121.15	1.55E+06	5.427	1.22E+03	4.85E-01	0.029424	8.02E-04
	150	650	114.44	1.38E+06	5.7275	6.46E+02	3.43E-01	0.061545	7.21E-05
	200	650	107.22	1.33E+06	8.7874	5.17E+02	2.98E-01	0.049315	7.42E-05
SiC	100	650	133.4	3.60E+06	3.6766	6.28E+03	7.57E+00	0.13473	0.000209
	150	650	130.52	3.03E+06	3.664	5.06E+03	1.27E+01	0.013574	0.000150
	200	650	128.12	2.94E+06	4.8716	4.61E+03	5.44E+00	0.13257	0.000212
MgZrO_3	100	650	112.4	1.36E+06	7.8197	2.39E+03	3.4177	0.05329	6.81E-05
	150	650	103.66	1.25E+06	12.859	1.56E+03	3.0906	0.034007	5.41E-05
	200	650	96.418	1.15E+06	17.213	1.28E+03	30482	0.062963	9.48E-05


CaZrO ₃	100	650	106.84	1.29E+06	26.061	2.93E+03	1.6808	0.5329	6.81E-05
	150	650	96.984	1.71E+06	8.4713	2.17E+03	4.8559	0.021826	7.12E-05
	200	650	88.943	1.07E+06	11.672	1.78E+03	2.9004	0.018575	8.06E-05
Mullite (3 Al ₂ O ₃ + 2SiO ₂)	100	650	134.67	4.24E+06	6.0452	4.24E+03	4.26	0.628232	6.27E-05
	150	650	132.27	3.54E+06	1.5031	3.37E+03	1.333	0.028402	5.97E-05
	200	650	128.52	2.28E+06	4.9191	2.28E+03	4.7949	0.01933	7.67E-05

Table 4 Complied Analysis report for Engine Valve in Close state


Valve Details	Coating Thickness (μm)	Temperature (°C)		Heat Flux (W/m ²)		Equivalent von-Mises Stress (MPa)		Strain	
		Max	Min	Max	Min	Max	Min	Max	Min
Uncoated SUH11	0	650	22.013	1.48E+06	5.827	1.81E+02	4.58E+00	0.0010039	3.98E-05
ZrO ₂ + 8% Y ₂ O ₃	100	650	22	1.48E+06	0.008805	2.16E+02	0.4935	0.017024	3.26E-05
	150	650	22	1.34E+06	0.010406	3.35E+02	2.25E-01	0.11382	5.45E-05
	200	650	22	1.26E+06	0.013971	4.27E+02	2.32E-01	0.010313	4.15E-05
SiC	100	650	22	1.77E+06	0.0092254	2.06E+03	3.23E-01	0.000475	7.31E-06
	150	650	22	1.65E+06	0.011707	1.96E+03	2.42E-01	0.004166	9.24E-06
	200	650	22	1.48E+06	0.0081463	1.78E+03	1.54E-01	0.008237	3.62E-06
MgZrO ₃	100	650	22	1.31E+00	0.0088223	2.90E+02	0.5908	0.005744	9.74E-06
	150	650	22	1.15E+06	0.010499	4.25E+02	3.64E-01	0.000486	6.79E-06
	200	650	22	1.00E+06	0.0078109	3.11E+02	7.42E-01	0.005736	1.34E-06
CaZrO ₃	100	650	22	1.22E+06	0.00088871	5.91E+02	0.43297	0.005922	1.05E-05
	150	650	22	1.07E+06	0.010489	4.89E+02	6.35E-01	4.90E-03	9.97E-06
	200	650	22	8.90E+05	0.0081051	4.31E+02	5.85E-01	0.005739	9.76E-06
Mullite (3 Al ₂ O ₃ + 2SiO ₂)	100	650	22	1.81E+06	0.0093545	7.71E+02	0.39981	0.005121	9.40E-06
	150	650	22	1.68E+06	0.01218	6.86E+02	3.97E-01	0.004704	1.02E-05
	200	650	22	1.60E+06	0.0889463	6.38E+02	5.63E-01	0.004451	1.09E-05

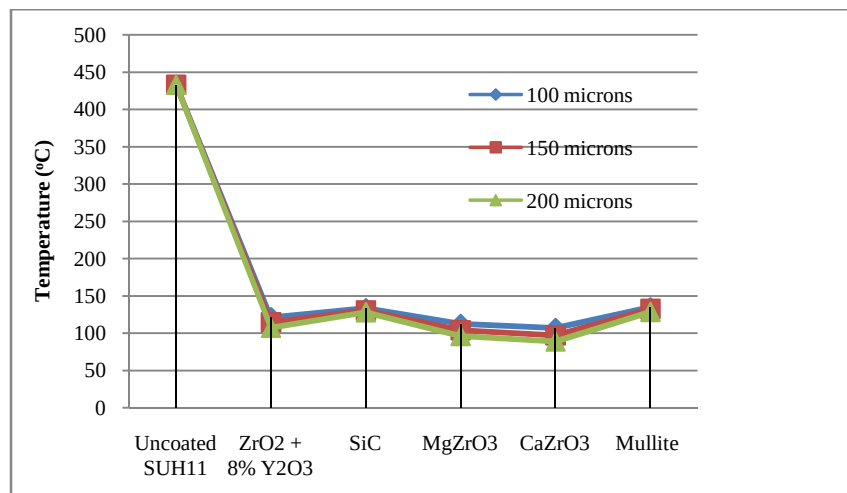


(a)

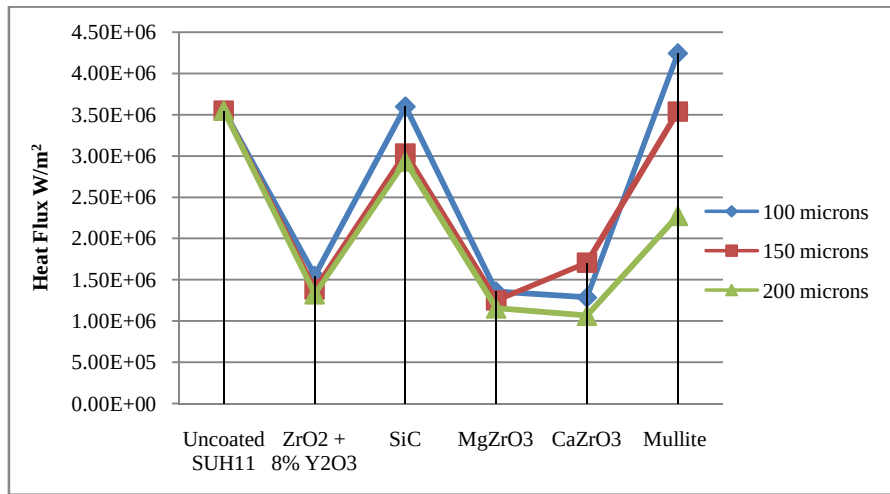

(b)

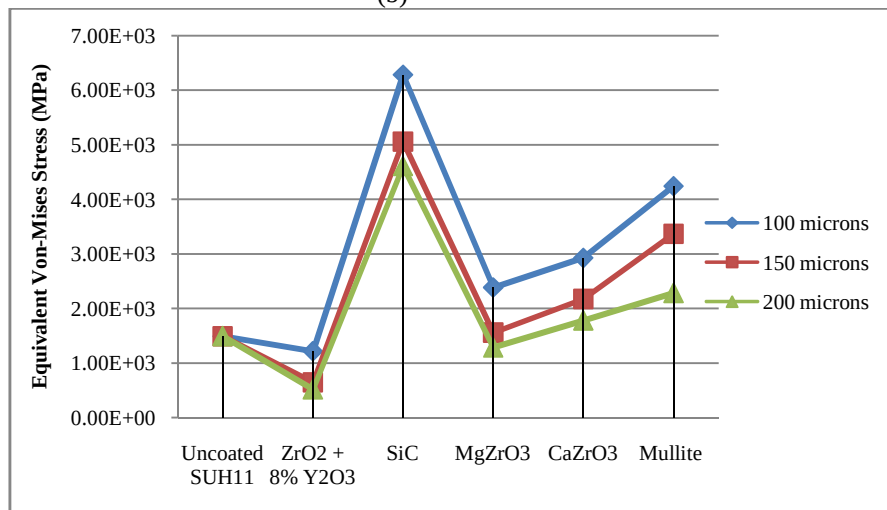

(c)

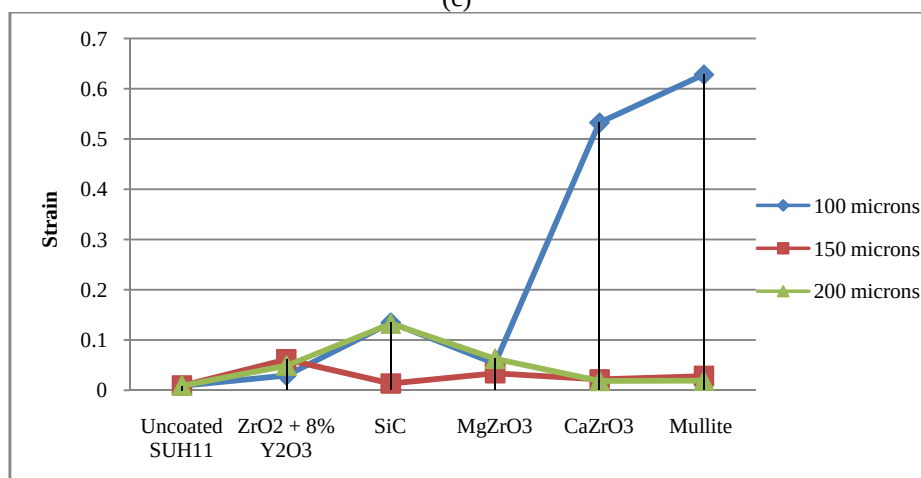

(d)

Figure 12 (a) Temperature fall plot
(c) Maximum Von-Mises stress plot

(b) Maximum heat flux plot
(d) Maximum strain plot

7. CONCLUSION

1. **Coating Effect:** Analysis Reports has shown considerable temperature fall for coated surfaces than in uncoated engine valve which in turn reduce thermal stresses and will also protect from thermal softening leading to wear of engine valve. Thus surface coating technology can be utilized for lower thermal stress and reducing erosive and corrosive wear to yield enhanced engine valve life and performance.
2. **Comparative database:** the study has provided the comparative database for 5 different coatings and also coatings has evaluated for different coating thickness. The results has revealed following points
 - CaZrO_3 surface coating gives best result at 200 microns for temperature fall and Stress and Strain with in material prescribed limit is most suitable surface coating.
 - CaZrO_3 surface coating shows high stress and strain values at 100 microns. Thus minimum coating thickness should be 150 microns and above.
 - MgZrO_3 and $\text{ZrO}_2 + 8\% \text{Y}_2\text{O}_3$ are second and third most suitable coatings with little difference in temperature fall and stress and strain within prescribed material limits.
 - $\text{ZrO}_2 + 8\% \text{Y}_2\text{O}_3$ coating can be used for lesser coating thickness with minor temperature rise due to less stress values.
 - SIC and Mullite shows almost similar results for temperature fall but both surface coats shows high stress values.

REFERENCES

- 1]. Ajay Pandey and R. K. Mandloi (2014), "Effects of High Temperature on the Microstructure of Automotive Engine Valves", Journal of Engineering Research and Applications www.ijera.com ISSN: 2248-9622, Vol. 4, Issue 3 (Version 1), March 2014, pp.122-126
- 2]. Anette M. Karlsson (2007), "Modeling Failures of Thermal Barrier Coatings", Layered, Functional Gradient Ceramics, and Thermal Barrier Coatings: Design, Fabrication and Applications, 333, pp. 155-165
- 3]. Borri C., Lavacchi A., Fossati A., Perissi I. and U. Bardi (2009), "Finite Element Analysis of Thermal Fatigue in Thermal Barrier Coatings (TBC)", COMSOL Conference 2009 Milan
- 4]. Christoffer Blomqvist (2014); "Thermal barrier coatings for diesel engine exhaust application", Degree project for Master of Science in engineering, mechanical engineering, Karlstad University
- 5]. Dabing LUO (2009), "Selection of coatings for tribological applications", thesis lecole centrale de lyon.
- 6]. Davis R Joseph (2004), "Hand book of thermal Spray technology", ASM international
- 7]. Ekrem Büyükkaya., Tahsin Engin and Muhammet Cerit (2006); "Effects of thermal barrier coating on gas emissions and performance of a LHR engine with different injection timings and valve adjustments", Energy Conversion and Management Volume 47, Issues 9–10, June 2006, Pages 1298–1310
- 8]. Erdinc Vural and Salih Ozer (2015), " Thermal Analysis of a Piston Coated with SiC and MgOZrO_2 Thermal Barrier Materials, International Journal of Scientific and Technological Research www.iiste.org ISSN 2422-8702 (Online) Vol 1, No.7, PP. 43-51
- 9]. Sharma, Subodh Kumar, and Ashish Kumar Sharma. "Mechanical vibration of orthotropic rectangular plate with 2D linearly varying thickness and thermal effect." International Journal of Research in Advent Technology 2.6 (2014): 184-90.
- 10]. Goli Udaya Kumar and Venkata Ramesh Mamilla (2013); "Failure analysis of internal combustion engine valves by using ansys", American International Journal of Research in Science, Technology, Engineering & Mathematics, 5(2), December 2013-February 2014, pp. 169-173
- 11]. Hart D., Harper D.H. and Gill M.J., "Case Studies in Wear Resistance Using HVOF, PTAW and Spray Fusion Surfacing" , Eutectic Canada Inc. Edmonton, Alberta, Canada G.R. Heath
- 12]. Sharma, Ashish Kumar, and Subodh Kumar Sharma. "A Quintic Spline Technique: Effect on Frequency of CSCS and SSSS Rectangular Plate with Varying Thickness and Temperature Effect." Romanian Journal of Acoustics and Vibration 13.1 (2016): 47.
- 13]. Heimann R.B. and Lehmann H. D., (2008), "Recently Patented Work on Thermally Sprayed Coatings for Protection against Wear and Corrosion of Engineered Structures", Vol. 1, pp. 41-55.
- 14]. Imdat Taymaz (2007), the effect of thermal barrier coatings on diesel engine performance, Surface & Coatings Technology, 20, 5249–5252
- 15]. Kuldeep Singh and Mandeep Kaur (2016), " Temperature Distribution on CaZrO_3 Coated Diesel Engine Piston with ANSYS", Special Issue on International Journal of Recent Advances in Engineering & Technology (IJRAET) V-4 I-2, PP. 83-86
- 16]. Marcin Białas (2008), "Finite element analysis of stress distribution in thermal barrier coatings", Elsevier Surface & Coatings Technology 202 (2008) 6002–6010



- 17]. McMahon, Cameron D., Scott, Murray L., (2002), "Innovative techniques for the finite element analysis and optimization of composite structures", International council of aeronautical Science 2002 congress.
- 18]. Nagaraj Nayak, Dani A D., Lakshminarayanan P., Gajendra Bab M K (2005), "Studies On Wear Of Inlet Valve And Cylinder Bore In Diesel Engines" , Proceedings of WTC2005 World Tribology Congress III September 12-16, 2005, Washington, D.C., USA
- 19]. Naresh Kr. Raghuwanshi, Ajay Pandey and R. K. Mandloi (2012); "Failure Analysis of Internal Combustion Engine Valves: A Review", International Journal of Innovative Research in Science, Engineering and Technology Vol. 1, Issue 2, December 2012, pp. 173-181
- 20]. P.M. Pierz (1993), "Thermal barrier coating development for diesel engine aluminium pistons", Surface and Coatings Technology Volume 61, Issues 1–3, 3 December 1993, Pages 60-66
- 21]. Piramanandhan M and N Mohanasundara Raju (2013), "Overview of recent research in thermal barrier coatings for internal combustion engines", International Journal of Conceptions on Mechanical and Civil Engineering Vol. 1, Issue. 1, pp. 93-100
- 22]. Promit Choudhury , Rahul Kumar Singh and Prithish Panda (2014), "Thermal and Structural Analysis of A Ceramic Coated Fsaе Brake Rotor Using 3d Finite Element Method for Wear Resistance and Design Optimisation", IOSR Journal of Mechanical and Civil Engineering (IOSR-JMCE), Volume 11, Issue 2 Ver. VII (Mar- Apr. 2014), PP 143-149
- 23]. Robert Vaben, Yutaka Kagawa, Ramesh Subramanian, Paul Zombo, and Dongming Zhu (2012), "Testing and evaluation of thermal-barrier Coatings", MRS bulletin, volume 37, October 2012 • www.mrs.org/bulletin.
- 24]. Rogerio Fernandes Brito, Solidonio Rodrigues de Carvalho, Sandro Metrevelle Marcondes de Lima Silva, Joao Roberto Ferreira (2009)," Thermal analysis in coated cutting tools", Elsevier International Communications in Heat and Mass Transfer 36 (2009) 314–321
- 25]. S. Krishnamani and T. Mohanraj (2016), "Thermal Analysis of Ceramic Coated Aluminum Alloy Piston using Finite Element Method", Indian Journal of Science and Technology, Vol 9(22) PP. 1-5
- 26]. S. M. Jafari, H.Mehdigholi, and M. Behzad(2014); "Valve Fault Diagnosis in Internal Combustion Engines Using Acoustic Emission and Artificial Neural Network", Hindawi Publishing Corporation Shock and Vibration Volume 2014, Article ID 823514, pp 1-9.